

NATURAL TYPE IA DIAMOND WITH GREEN-YELLOW COLOR DUE TO NI-RELATED DEFECTS

Wuyi Wang, Matthew Hall, and Christopher M. Breeding

Commonly seen in HPHT-grown synthetic diamonds with a green component, nickel-related defects were identified for the first time in a type Ia natural diamond with a strong green component. The 1.75 ct Fancy green-yellow diamond showed a strong peak at 1332 cm^{-1} in the IR absorption spectrum, strong absorption from the 1.40 eV center and the associated $\sim 685\text{ nm}$ band in the Vis-NIR spectrum, and extremely strong emissions from Ni-related defects in the photoluminescence spectra—all of which proved that nickel was the primary cause of the green color.


Nickel is widely used as a catalyst in high-pressure, high-temperature (HPHT) synthetic diamond growth processes. Consequently, Ni-related lattice defects are common in HPHT-grown synthetic diamonds, and can produce a green color component when the nitrogen concentration is sufficiently low (Lawson et al., 1998). The occurrence of trace amounts of Ni has also been confirmed in some natural diamonds—including, but not limited to, chameleon diamonds, yellow-orange diamonds colored by a broad absorption band at $\sim 480\text{ nm}$, H-rich diamonds, and even some colorless type IIa diamonds (Shigley et al., 2004; Hainschwang et al., 2005; and the present authors' unpublished research).

In a recent study, Wang and Moses (2007) provided the first evidence of Ni-related defects producing green color in a natural gem diamond: a 2.81 ct type IIa Fancy Intense yellowish green oval cut. However, the general role of Ni as a color-producing center in many natural diamonds remains unclear. Soon after studying the type IIa diamond noted above, GIA's New York laboratory examined a type

Ia natural diamond with a strong green color component that also proved to be the result of Ni-related defects.

Materials and Methods. A 1.75 ct cushion-cut diamond (figure 1) was submitted to the New York laboratory for a grading report and color graded Fancy green-yellow. To fully document that both the stone and the color were natural, we conducted standard gemological testing, fluorescence imaging (Diamond Trading Company [DTC] DiamondView), and detailed spectroscopic testing. Infrared absorption spectra were collected using a Thermo 6700 Fourier-transform infrared (FTIR) spectrometer ($6000\text{--}400\text{ cm}^{-1}$, 1 cm^{-1} resolution, up to 1,024 scans, at room temperature). UV-visible-near infrared (UV-Vis-NIR) spectra were collected with an Ocean Optics high-resolution spectrometer (Model HP-2000+, $250\text{--}1000\text{ nm}$, 1 nm resolution, deu-

Figure 1. This 1.75 ct cushion-cut Fancy green-yellow diamond is colored mainly by Ni-related defects. Photo by Jian Xin (Jae) Liao.

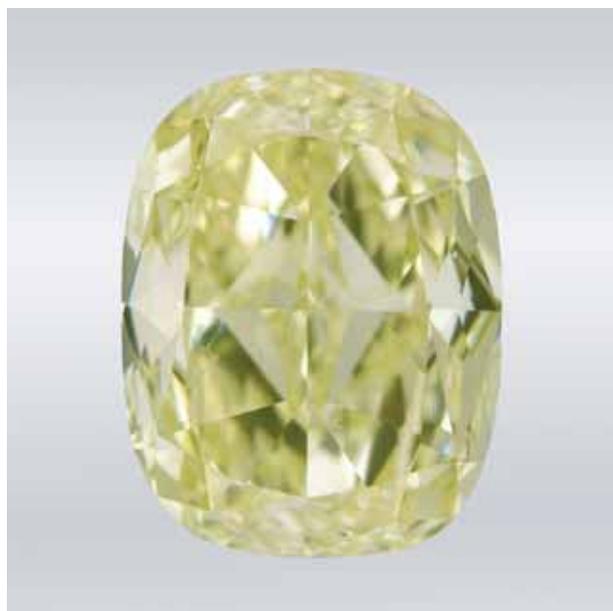

See end of article for About the Authors and Acknowledgments.

GEMS & GEMOLOGY, Vol. 43, No. 3, pp. 240–243.

© 2007 Gemological Institute of America

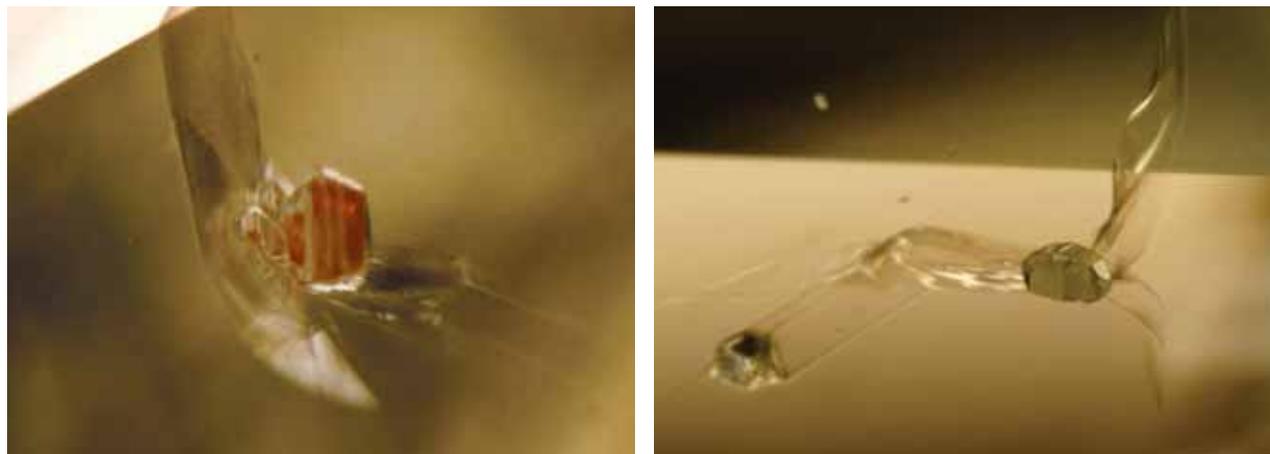


Figure 2. The presence of included crystals of reddish orange almandine-rich garnet (left, image width 0.98 mm) and pale green omphacite (right, image width 0.65 mm) demonstrates that this natural diamond crystallized in an eclogitic environment. Photomicrographs by W. Wang.


terium-tungsten-halogen source, at liquid-nitrogen temperature). Photoluminescence and Raman spectra were collected using a Renishaw inVia Raman microscope (488, 514, 633, and 830 nm laser excitations, various scan ranges, at liquid-nitrogen temperature). To test the diamond's color stability and any possible thermochromic properties, we heated it with an alcohol lamp to a temperature of $\sim 350^{\circ}\text{C}$.

Results and Discussion. Observation with a gemological microscope indicated that the green-yellow color was distributed evenly throughout the stone, with no evidence of treatment visible. Microscopy also revealed colorful euhedral mineral inclusions (100–150 μm in longest dimension) that were surrounded by small fractures. The reddish orange and pale green crystals (figure 2) were identified as almandine-rich garnet and omphacite, respectively, by Raman spectroscopy. These inclusions are typical of diamonds from eclogitic environments (Meyer, 1987; Koivula, 2000). The presence of natural mineral inclusions proved that the diamond was not synthetic. Furthermore, careful microscopic examination with various lighting configurations confirmed no coating was present.

The diamond fluoresced strong orangy yellow to long-wave UV radiation and moderate greenish yellow to short-wave UV; we observed no phosphorescence with standard handheld gemological UV lamps. When examined with the DTC DiamondView, the stone showed a large variation in fluorescence (figure 3). Some zones displayed unevenly distributed linear green luminescence features. Other regions showed moderate greenish yellow luminescence. Still other parts of the stone displayed banded blue fluorescence. Weak greenish yellow phosphorescence was also observed at the ultra-short wavelengths. The large variation in fluorescence colors and the absence of a typical HPHT-synthetic diamond growth pattern confirmed that this stone was natural.

The infrared absorption spectrum showed a clear band at 1282 cm^{-1} , indicating the diamond was type IaA; the nitrogen concentration was calculated to be about 36 ppm. Distinct absorption peaks were also noted at 3107 and 1405 cm^{-1} , showing the occurrence of hydrogen impurities. A relatively strong peak at 1332 cm^{-1} suggested that N^+ (which sometimes serves as a proxy for Ni content in diamond) might also be present. Isolated substitutional nitrogen acts as an electron donor, and some nickel-related defects are observed in the negatively charged state (Lawson et al., 1998). A strong 1332 cm^{-1} absorption is consistent with the detection of Ni-related defects in this diamond.


Figure 3. The green-yellow diamond showed distinctive zoned fluorescence in the DiamondView that also ruled out a synthetic origin. Areas of green, greenish yellow, and blue fluorescence occurred in different parts of the diamond. Image by W. Wang.

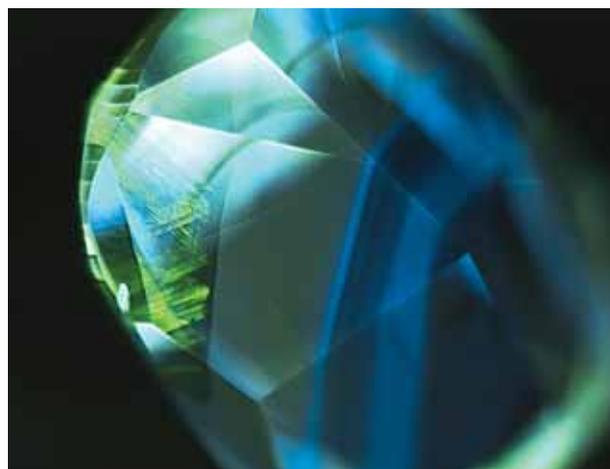

The Vis-NIR absorption spectrum (figure 4) showed weak but distinct absorptions between 350 and 370 nm (357.0, 360.2, 363.5, 367.0 nm; not shown in the figure due to the high UV background) and between 460 and 480 nm (468.0, 473.3, 477.4 nm). These series of peaks are known to originate from Ni-related defects (Collins and Stanley, 1985; Lawson and Kanda, 1993a; Yelisseyev et al., 1996). They are identical to those reported for the type IIa, Ni defect-colored yellowish green diamond seen previously (Wang and Moses, 2007). Unlike the type IIa diamond, however, this type Ia stone exhibited additional weak absorptions at 415.2 nm (zero-phonon line [ZPL] of the N3 center) and 427.1 nm, but it lacked features in the 600–650 nm range (608.1, 637.5, 642.5 nm). An outstanding characteristic of the Vis-NIR absorption spectrum of the type Ia green-yellow diamond was the strong absorption of the 1.40 eV center (unresolved ZPL doublet at ~884 nm) and the associated ~685 nm band; these are likely caused by interstitial Ni⁺ (Isoya et al., 1990; Lawson and Kanda, 1993b). We also observed a sharp peak at 793.0 nm, another well-known Ni-related defect, but it was much weaker than the 884 nm peak. The 685 nm band was strong and broad, extending from 585 nm to about 735 nm, and efficiently blocked the transmission of red and orange light. Combined with a gradual increase in absorption from ~555 nm to the high-energy (low-wavelength) side due to unknown causes, the 685 nm absorption generated a transmission window centered at ~555–585 nm that resulted in the observed green-yellow bodycolor.

The photoluminescence spectrum collected with 830 nm laser excitation was dominated by the 883.1/884.8 nm doublet (i.e., the 1.40 eV center; figure 5). When 514 nm

Figure 4. Strong absorption from the 1.40 eV center (ZPL at ~884 nm) and the associated ~685 nm band are the dominant features in the Vis-NIR absorption spectrum of the 1.75 ct Fancy green-yellow diamond. The 1.40 eV center, which is due to interstitial Ni⁺, is the main cause of the diamond's green component.

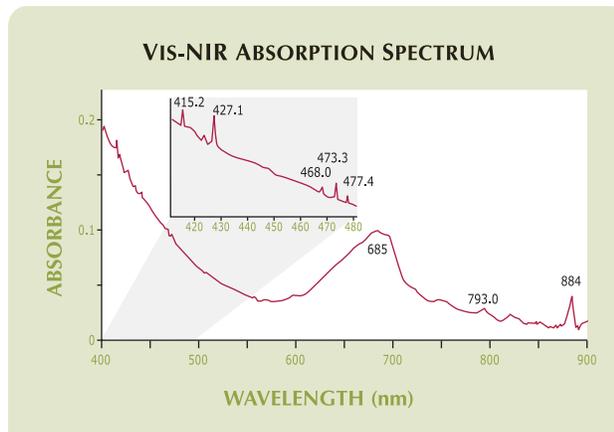


laser excitation was used, the spectrum exhibited a broad band centered at ~640 nm, with numerous sharp emissions superimposed between 560 and 760 nm. These PL features are typically associated with the broad 480 nm absorption band that occurs in some natural yellow-to-orange diamonds and all chameleon diamonds, both of which reportedly contain Ni-related defects (Collins, 2001). However, these features are not believed to correlate directly with the 1.40 eV center. Unlike the green-yellow stone presented here, those types of diamonds do not show Ni-related defects in the Vis-NIR absorption spectrum. Spectroscopy also revealed that some common defects in type Ia natural diamonds (e.g., H3, H4, N-V centers) were not detected in this diamond.

Green color in natural diamonds can be introduced by a number of known defects or defect combinations, including absorptions from GR1, H2, and some hydrogen-related defects, and/or the luminescence of the H3 defect (Collins, 1982, 2001). The absence of any of these centers and the almost exclusive occurrence of Ni-related defects (in particular the 1.40 eV center), strongly indicate that the green component of this diamond is caused by Ni.

A final interesting property of the green-yellow diamond is that when heated (~350°C), the stone changed color slightly to a more yellow (less green) hue. After approximately 15 seconds, the original color was restored when we cooled the stone at room temperature. This weak thermochromism, together with other gemological and spectro-

Figure 5. PL spectra confirmed the presence of extremely strong emissions from Ni-related defects (e.g., the 883.1/884.8 nm doublet). Numerous sharp emissions in the range 560–760 nm and a very broad luminescence band centered at ~640 nm strongly indicate an association between this diamond and natural yellow-orange and chameleon diamonds, which exhibit broad 480 nm absorption bands. The 640 nm feature is an emission band of an unknown defect that caused very weak absorption at ~480 nm.

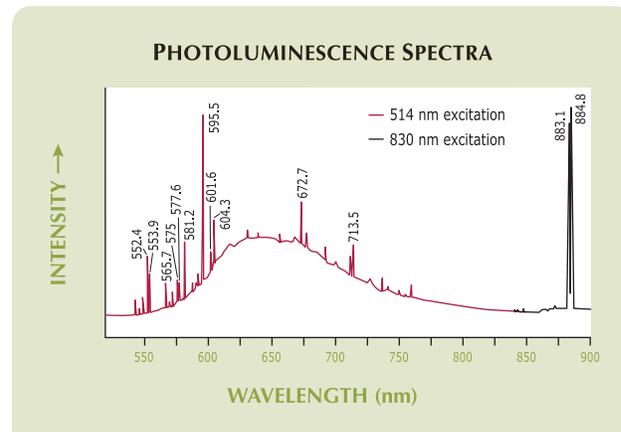

scopic similarities between this stone and chameleon diamonds, may indicate that Ni-related defects play a role in the thermochromic and photochromic diamond properties exhibited by both of these unusual types of diamonds.

Conclusions. Spectroscopic evidence from this rare type Ia gem diamond, as well as the yellowish green type IIa stone described recently, proves that Ni-related defects are directly responsible for the green component of the bodycolor. Diamonds colored by Ni may, in fact, be more common than has been believed, as reexamination of previously collected spectra seems to indicate. Therefore, nickel-related defects may represent another important cause of green color in natural diamonds.

ABOUT THE AUTHORS

Dr. Wang is manager of research projects, and Mr. Hall is manager of Identification Services, at the GIA Laboratory in New York. Dr. Breeding is a research scientist at the GIA Laboratory in Carlsbad, California.

ACKNOWLEDGMENTS

The authors thank Dr. James Butler (Naval Research Laboratory, Washington, DC) and Dr. Mark Newton and Dr. Christopher Welbourn (University of Warwick, UK) for their constructive comments and suggestions, which helped improve this article significantly. We are grateful to Thomas Moses (GIA Laboratory, New York) for discussions.

REFERENCES

- Collins A.T. (1982) Colour centres in diamond. *Journal of Gemmology*, Vol. 18, pp. 37–75.
- Collins A.T. (2001) Colour of diamond and how it may be changed. *Journal of Gemmology*, Vol. 27, No. 6, pp. 341–359.
- Collins A.T., Stanley M. (1985) Absorption and luminescence studies of synthetic diamond in which the nitrogen has been aggregated. *Journal of Physics D*, Vol. 18, No. 12, pp. 2537–2545.
- Hainschwang T., Simic D., Fritsch E., Deljanin B., Woodring S., DelRe N. (2005) A gemological study of a collection of chameleon diamonds. *Gems & Gemology*, Vol. 41, No. 1, pp. 20–35.
- Isoya J., Kanda H., Uchida Y. (1990) EPR studies of interstitial Ni centers in synthetic diamond crystals. *Physical Review B*, Vol. 42, No. 16, pp. 9843–9852.
- Koivula J.I. (2000) *MicroWorld of Diamonds*. Gemworld International, Northbrook, IL.
- Lawson S.C., Kanda H. (1993a) An annealing study of nickel point defects in high-pressure synthetic diamond. *Journal of Applied Physics*, Vol. 73, No. 8, pp. 3967–3973.
- Lawson S.C., Kanda H. (1993b) Nickel in diamond: An annealing study. *Diamond and Related Materials*, Vol. 2, No. 2–4, pp. 130–135.
- Lawson S.C., Fisher D., Hunt D.C., Newton M.E. (1998) On the existence of positively charged single-substitutional nitrogen in diamond. *Journal of Physics: Condensed Matter*, Vol. 10, pp. 6171–6180.
- Meyer H.O.A. (1987) Inclusions in diamond. In P. H. Nixon, Ed., *Mantle Xenoliths*, Wiley, Chichester, UK, pp. 501–523.
- Shigley J.E., Wang W., Moses T., Hall M. (2004) Photoluminescence features of chameleon diamonds. *Proceedings of the 55th De Beers Diamond Conference*, Coventry, England, pp. 4.1–4.2.
- Wang W., Moses T. (2007) Lab Notes: Type IIa diamond with intense green color introduced by Ni-related defects. *Gems & Gemology*, Vol. 43, No. 2, pp. 156–158.
- Yelissev A., Nadolnny V., Feigelson B., Terentyev S., Nosukhin S. (1996) Spatial distribution of impurity defects in synthetic diamonds obtained by BARS technology. *Diamond and Related Materials*, Vol. 5, No. 5, pp. 1113–1117.



Give the gift of knowledge.

Whether it's the young family member just starting their gemology education or the client you've done business with for decades, we're sure there's someone on your list who would love a gift subscription to *Gems & Gemology*. Order now and we'll even include this personalized gift card. And if you've got a long gift list, ask about our special rates for bulk subscription orders.

GEMS & GEMOLOGY.
The Quarterly Journal That Lasts A Lifetime

To order, visit www.gia.edu/gemsandgemology and click on *Gift Subscriptions*.
Call 800-421-7250 ext. 7142 within the U.S., or 760-603-4000 ext. 7142.